



REVISTA TÉCNICA

DE LA FACULTAD DE INGENIERÍA

Una Revista Internacional Arbitrada
que está indizada en las publicaciones
de referencia y comentarios:

- SCOPUS
- Compendex
- Chemical Abstracts
- Metal Abstracts
- World Aluminium Abstracts
- Mathematical Reviews
- Petroleum Abstracts
- Current Mathematical Publications
- MathSci
- Revenct
- Materials Information
- Periódica
- Actualidad Iberoamericana

UNIVERSIDAD DEL ZULIA



Quiébranos de la Facultad de Ingeniería de la Universidad del Zulia

Patrimonio del Estado Zulia e
interés Cultural desde 2001

Fecha de Construcción:
1954-1958

Diseño: Arquitecto Carlos Raúl
Villanueva, con elementos
novedosos de adaptación
climática.

Policromía de la obra: Artista
Zuliano Víctor Valera.

Antibacterial property of cancrinite-type zeolites exchanged with silver and copper cations

Freddy Ocanto^{1*}, Carlos F. Linares¹, Edith Figueredo^{1,2}, Caribay Urbina de Navarro³

¹Unidad de Síntesis de Materiales y Metales de Transición, Departamento de Química, Facultad Experimental de Ciencias y Tecnología, Universidad de Carabobo, Apartado 3336, Valencia 2005, Venezuela.

²Laboratorio de Calidad Ambiental, Escuela de Ingeniería Civil, Facultad de Ingeniería, Universidad de Carabobo, Apartado Postal 3336, Valencia 2005, Venezuela.

³Centro de Microscopía Electrónica Dr. Mitsuo Ogura, Escuela de Biología, Facultad de Ciencias, Universidad Central de Venezuela, Apartado 20513, Caracas 1020-A, Venezuela.

*Autor de correspondencia: ocantow@gmail.com

<https://doi.org/10.22209/rt.v42n3a06>

Recepción: 22/08/2018 | Aceptación: 05/06/2019 | Publicación: 01/09/2019

Abstract

Ag⁺, Cu²⁺ or Ag⁺-Cu²⁺ ion-exchanged nitrate-sodium cancrinite-type zeolites were tested as bactericidal agents against *Escherichia coli* (*E. coli*) and *Pseudomonas aeruginosa* (*P. aeruginosa*). Nitrated-sodium cancrinite was synthesized using solutions of NaOH and NaNO₃, and using zeolite X as Al and Si sources under hydrothermal conditions at 80 °C and autogenous pressure during 40 h. Solids were characterized by powder X-ray diffraction (XRD), Fourier transformed infrared spectroscopy (FT-IR), scanning electron microscopy (SEM) and chemical analysis. Then, different masses of these ion-exchanged zeolites were mixed with the microorganisms. Results showed that *E. coli* was more sensitive than *P. aeruginosa*, and 2.5 mg of Ag⁺ or Cu²⁺-Ag⁺ cancrinites were enough to inhibit the *E. coli* growth, while for *P. aeruginosa* larger amounts of Ag⁺ (5 mg) and Ag⁺-Cu²⁺ (20 mg) of the cancrinites were necessary. Cu-zeolites did not show bactericidal activity. Different treatments times between these microorganisms and the modified zeolites were also investigated. A 20 min treatment was enough to inhibit totally the bacterial growth. As a reference system zeolite A exchanged with these metals was used.

Keywords: nitrate cancrinite, silver, antibacterial, *E. coli*, *P. aeruginosa*.

Propiedad antibacteriana de zeolitas tipo cancrinita intercambiadas con iones plata y cobre

Resumen

Se estudiaron zeolitas tipo cancrinita sódica-nitrada intercambiadas con Ag⁺, Cu²⁺ o Ag⁺-Cu²⁺ como agentes bactericidas contra *Escherichia coli* (*E. coli*) y *Pseudomonas aeruginosa* (*P. aeruginosa*). La zeolita sódica-nitrada fue sintetizada utilizando soluciones de NaOH, NaNO₃, y zeolita X como fuente de Al y Si en condiciones hidrotérmica, 80 °C, presión autógena durante 40 h. Los sólidos fueron caracterizados por difracción de rayos X de polvo (DRX), espectroscopia de infrarrojo con transformada de Fourier (FT-IR), microscopía electrónica de barrido (MEB) y análisis químico. Diferentes masas de zeolitas intercambiadas fueron puestas en contacto con estos microorganismos. Los resultados mostraron que la *E. coli* es más sensible que la *P. aeruginosa* y 2,5 mg de la cancrinita intercambiada con Ag⁺ o Ag⁺-Cu²⁺ fue suficiente para controlar la población completa del microorganismo. Sin embargo para controlar la población de la *P. aeruginosa*, se necesitó una cantidad mayor de la cancrinita modificada Ag⁺ (5 mg) y Ag⁺-Cu²⁺ (20 mg). Las zeolitas intercambiadas con cobre no presentaron actividad bactericida. Se estudió el efecto de diferentes tiempos de contacto entre estos microorganismos y las zeolitas modificadas; encontrándose que a los 20 minutos un efecto bactericida. Zeolitas A intercambiadas con estos mismos metales fueron usadas como referencia.

Palabras claves: nitrato-cancrinita, plata, antibacteriana, *E. coli*, *P. aeruginosa*.

Introduction

Cancrinites are special zeolites conformed by small cages (ϵ -cages) distributed in a hexagonal structure and a big channel of 12 rings along the direction of the hexagonal c axis of the structure, forming one-dimensional rectilinear channels along this axis. Access to these channels occurs through windows formed by 12 member rings [1]. Usually, anionic species such as: nitrate, sulfate, oxalate, thiosulfate, etc., are found inside of the big channel of the structure compensating the positive charge generated by sodium cations placed in the ϵ -cages [2-4]. Due to the blocking of pores by anions inside of the cancrinite's structure, few pharmaceutical or industrial applications have been reported in the literature [5-7].

Sodium-zeolite, *per se*, do not have bactericide effect but several ion-exchanged cations in its structure are active as bactericidal agents. Due to the fact that cancrinite-type zeolites show a Si/Al ratio close to 1, they could be good candidates to be exchanged with cations such as Ag^+ or Cu^{2+} which are recognized antibacterial agents.

Likewise, Rivera-Garza [8] studied a mexican natural zeolite (clinoptilolite-heulandite) exchanged with different Ag^+ proportions. These modified zeolites were tested as antibacterial agents in contaminated waters with *Escherichia coli* and *Streptococcus faecalis*. Results showed that both bacteria could be eliminated at the highest used silver amount after 2 h of contact time.

Milán [9] modified natural clinoptilolites with different heavy metals (Ni^{2+} , Zn^{2+} , Fe^{3+} and Cu^{2+}). These zeolites were tested on pure cultures of *E. coli* and *P. aeruginosa*. Results established a decreasing order of the bactericidal capacity being $\text{Cu}^{2+} > \text{Fe}^{3+} > \text{Zn}^{2+} > \text{Ni}^{2+}$.

Otherwise, Inoue [10] found that silver-loaded zeolites had a strong bactericidal activity against *E. coli*. Dissolved oxygen in the culture medium was an essential factor for the occurrence of the bactericidal activity because it was only observed under aerated condition.

Other zeolites and cations have also been used in medical applications [11, 12], environmental management in shrimp aquaculture [13] and bactericidal agents for water disinfection [14, 15]; however, cancrinite-type zeolites have been few mentioned for this last purposes [16, 17], basically because they have a low ion-exchange capacity. Their low ion-exchange capacity is due to the blocking of pores by anions inside of the main channels. However, this can be profitable taking into account that several cations, such as silver, can act as bactericide even at low concentrations. Therefore, it could reduce the reactant amount and avoid environmental troubles.

Although zeolites act as metal carriers they do not show *per se* antibacterial effects. The metallic load depends on the Si/Al ratio: zeolites A and X have a high

exchanged capacity because their Si/Al ratio is closed to 1; cancrinite-type zeolites have a Si/Al ratio close to 1 also, but they have a low exchanged capacity, this could be interesting because these antibacterial metals act at low concentrations saving costs and avoiding damages to the environment.

The aim of this paper was to modify cancrinite-type zeolites with silver, copper, and a silver-copper mixture and then test them as possible antibacterial agents against *E. coli* and *P. aeruginosa*. Likewise, an exchanged zeolite A with the same cations was also used as reference. Antibacterial properties of these solids depend on the Si/Al ratio which is the same for both zeolites.

Experimental Section

Synthesis of sodium-nitrate cancrinite

A nitrate cancrinite-type zeolite was synthesized according to the previously reported procedure [18]: 7.5 g NaNO_3 were dissolved into 50 mL of distilled water in a teflon reactor. Then, 10 g NaOH were added and dissolved and finally 5 g zeolite X were also added to this solution forming a slurry. This reactor was sealed and put in a convection oven at 80 °C for 110 h. Samples were filtered and washed with enough distilled water until a pH near 7.

Ion-exchange procedure

The synthesized nitrated-sodium cancrinite was ion-exchanged with silver, copper and a mixture of silver-copper cations. 15 mL of solution (0.02M) of Ag^+ , Cu^{2+} or and Ag^+ - Cu^{2+} mixture were added to 5 g of sodium-nitrate cancrinite forming a slurry. This slurry was agitated at 80 °C for 24 h in nitrogen atmosphere in the absence of light. The slurries were filtered off and supernatants were discarded. The filtered solids were kept for a new ion-exchange. This procedure was repeated three times. After that, solids were washed up with abundant distilled water, filtered and dried for 110 h at 80 °C.

Characterization of modified cancrinites

Ion-exchanged cancrinites with Ag^+ , Cu^{2+} and a Ag^+ - Cu^{2+} mixture were characterized by powder-X-ray diffraction (XRD), Fourier transformed infrared spectroscopy (FT-IR), chemical analysis and scanning electron microscopy (SEM).

XRD analyses were carried out by using a Siemens 5000 diffractometer with a $\text{CuK}\alpha$ radiation (1.542 Å) for crystalline phase detection between 5 and 50° (2 θ). The presence of functional groups and evaluation of solids purity were achieved by FTIR; spectra were recorded in a Perkin-Elmer 283 spectrometer in the 4000-400 cm^{-1} range. Samples were prepared by mixing the solids with KBr to form a thin pastille. The morphology of the products was observed on a Hitachi FEG-4500 scanning

electron microscope (SEM) with 10 KeV of acceleration. Samples were dispersed over a conductive surface and covered with a thin gold film.

Assay of bactericidal activity

E. coli and *P. aeruginosa* were used to assess the bactericidal activity of Ag^+ , Cu^{2+} and $\text{Ag}^+\text{-Cu}^{2+}$ modified cancrinites and zeolites A. These bacteria were collected from the Department of Microbiology (University of Carabobo). Brain-heart infusion was used as an aerobic growing medium for both microorganisms at 35 °C. Once microorganisms reached the exponential growing phase of cultures (after 18 h), an aliquot of this suspension was diluted in a Mueller-Hinton culture medium to get approximately 1.5×10^8 units of colonies per plate (CFU). Then, 0.001 mL from this suspension was inoculated in 9.999 mL of Mueller-Hinton culture medium to get a 1×10^{-4} dilution factor (1.5×10^6 CFU). In order to determine the CFU, 100 μL from this medium were spread on a Mueller-Hinton agar plate and incubated at 35 °C for 24 h [19].

Influence of zeolite mass

Among 2.5 and 125 mg of modified zeolites were mixed with 2 mL from a 10^{-4} diluted solution containing *E. coli* or *P. aeruginosa*. Samples were horizontally agitated for 6 h and then, slurries were kept in static condition for 24 h. After that, an aliquot of 100 μL , was spread on a Mueller-Hinton agar plate and incubated at 35 °C for 24 h. Finally, the CFU was determined after contact with modified zeolites.

Influence of contact time

To study the contact time among modified zeolites and the microorganisms 5 and 20 mg of modified zeolites were mixed with 2 mL of a 10^{-4} diluted solution containing *E. coli* or *P. aeruginosa*.

Samples were horizontally agitated during different contact times (14-1440 min), and aliquots of 100 μL were spread on a Mueller-Hinton agar plate and incubated at 35 °C for 24 h. Finally, the CFU was determined for each contact time.

Results and discussion

Characterization of sodium-nitrate cancrinite

XRD analysis (Fig 1) showed reflections attributed to the nitrated-cancrinite zeolite that were consistent with the P63 spatial group [20]. This diffraction pattern shows intense peaks corresponding to (110), (101), (210), (300), (211), (400), (311), (102) and (330) planes which are representatives of the nitrated-cancrinite zeo-

lites (PDF 46-1332) [21, 22]. Other phases such as sodalite were not present in the synthesized sample.

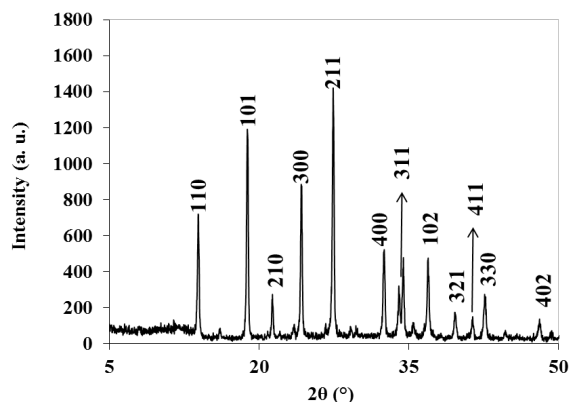


Figure 1. XRD pattern of nitrate-sodium cancrinite-type zeolite.

Fig. 2 shows the FTIR spectrum of the synthesized cancrinite-type zeolite. A series of characteristic bands could be identified [23, 24]: A band between 3500 and 3400 cm^{-1} corresponds to OH^- groups from water molecules entrapped inside of the framework. While the band at 1639 cm^{-1} corresponds to water molecules inside of the framework.

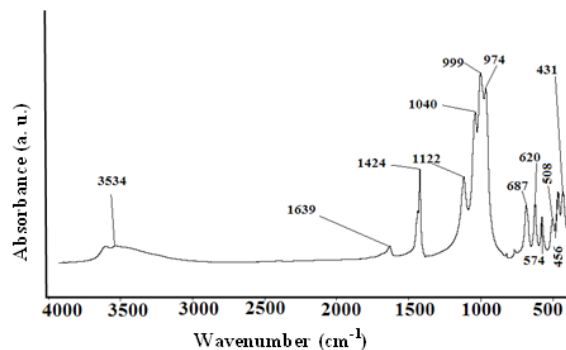


Figure 2. FT-IR spectrum of sodium-nitrate cancrinite-type zeolite.

A band at 1424 cm^{-1} was assigned to occluded nitrate anions as counter-anion in the internal cavities of the cancrinite zeolite. Bands in the region between 1122 and 974 cm^{-1} have been assigned to Si-O-Al asymmetric stretch vibrations of framework species. Three bands between 687 and 574 cm^{-1} , called "cancrinite fingerprint" correspond to Si-O-Al symmetric stretch vibration bonds.

SEM analysis of the synthesized zeolite showed the presence of small hexagonal prismatic crystallites (~2 μm) of cancrinite zeolite (Fig. 3). These prismatic crystallites correspond to the cancrinite zeolite in agreement with Barnes [25].

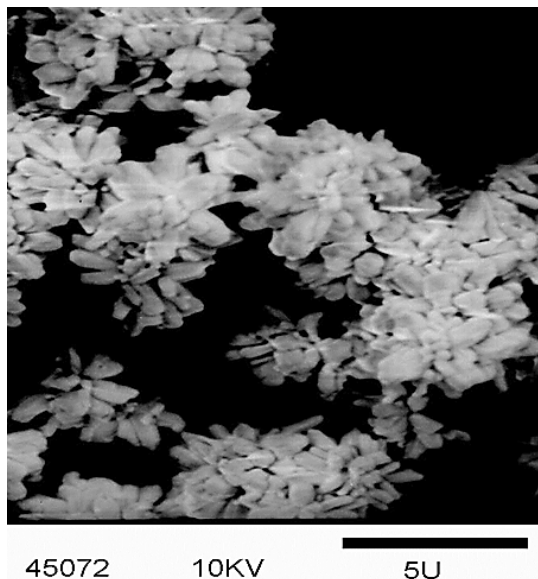


Figure 3. SEM of nitrate-sodium cancrinite type zeolite. Typical hexagonal crystals can be observed.

The Si/Al ratio and formula of zeolites were determined by chemical analyses (Table 1). A Si/Al ratio ≈ 1 was obtained for both zeolites (cancrinite and zeolite A) which agree the revised literature [1].

This Si/Al ratio was higher for the cancrinite zeolite than for the zeolite A. Experimental errors could be associated to these results. A similar Ag^+ and Cu^{2+} ion-exchange amount was obtained for both zeolites. These results allowed a better comparison for these solids when they were used as antibacterial materials. The amount of exchanged Ag was superior to that of Cu. These results are associated to the cation oxidation state. For each Al^{3+} ion from the Al-O-Si zeolite framework as possible to exchange one Ag^+ cation while two Al^{3+} were replaced for one Cu^{2+} ions in order to get the neutrality of the framework. Likewise, the metal ion-exchanged percentage (Ag^+ or Cu^{2+}) was very low. This result is due to the blocking of the pores in the cancrinite zeolite and the small pore size of the zeolite A structure as was previously mentioned [1].

Table 1. Chemical analysis of the exchanged zeolites, chemical formula and exchange percentage.

Solids	Empirical formula	%Ag(p/p)	%Cu(p/p)	Si/Al
ZA-Ag/Cu	$\text{Na}_{91.06}\text{Ag}_{2.21}\text{Cu}_{0.73}\text{Al}_{94.72}\text{Si}_{97.28}\text{O}_{384}$	1.3 ± 0.1	0.57 ± 0.06	1.03
ZA-Cu	$\text{Na}_{92.08}\text{Cu}_{0.97}\text{Al}_{94.02}\text{Si}_{97.80}\text{O}_{384}$		0.69 ± 0.02	1.04
ZA-Ag	$\text{Na}_{92.73}\text{Ag}_{2.07}\text{Al}_{94.80}\text{Si}_{97.80}\text{O}_{384}$	1.3 ± 0.1		1.03
Can-Ag	$\text{Na}_{7.57}\text{Ag}_{0.09}\text{Al}_{5.66}\text{Si}_{6.34}\text{O}_{24}(\text{NO}_3)_2$	1.5 ± 0.2		1.12
Can-Ag/Cu	$\text{Na}_{7.30}\text{Ag}_{0.16}\text{Cu}_{0.07}\text{Al}_{5.60}\text{Si}_{6.40}\text{O}_{24}(\text{NO}_3)_2$	1.6 ± 0.1	0.74 ± 0.07	1.14
Can-Cu	$\text{Na}_{7.44}\text{Cu}_{0.07}\text{Al}_{5.58}\text{Si}_{6.42}\text{O}_{24}(\text{NO}_3)_2$		0.83 ± 0.06	1.15

ZA: zeolite A. Can: cancrinite

Influence of zeolite mass on the bacterial strains.

Escherichia coli

Tables 2 and 3, shows the CFU of *E. coli* and *P. aeruginosa* determined on Mueller-Hinton agar plates before and after contact with different amounts of modified cancrinite zeolite or zeolite A. Results showed that those ion-exchanged zeolites with Ag^+ or $\text{Ag}^+\text{-Cu}^{2+}$ were more effective than those exchanged with Cu^{2+} . 2.5 mg of these modified Ag^+ zeolites were enough to kill the whole bacteria population after 24 h of contact (Fig 4a); while 50 mg or more (125 mg) of Cu^{2+} modified zeolites were not able to control the proliferation of *E. coli*. It is probably that, at the assayed concentrations, the presence of Cu^{2+} cations does not have effect against *E. coli* population (Fig 4b). Ag^+ and Cu^{2+} cations have been reported as antibacterial materials [8, 9].

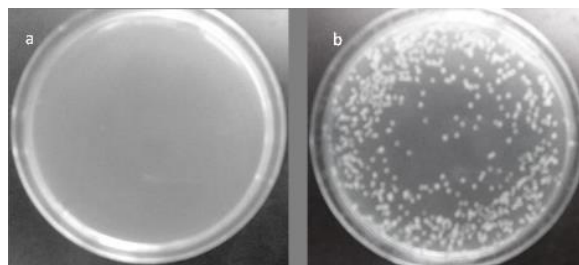


Figure 4. a) Bacterial growth on the agar plates containing 2.5 mg of Ag zeolites, after 24 h incubation b) 50 mg of Cu^{2+} modified zeolites, after 24 h incubation.

However, several microorganisms show an increasing tolerance to copper, which is induced by resistance mechanisms, where copper resistant species appear [9]; moreover, low Cu^{2+} concentrations in the culture medium are also necessary as a micronutrient for bacteria [19].

According to our results, Cu^{2+} cations, from Cu-loaded zeolites, do not have effect against *E. coli* or, on the contrary, helps the vitality of this organism. Likewise, Ag^+ cations were very effective against this organism even in presence of Cu^{2+} cations which, according to our results,

Table 2. CFU of *E. coli* determined on Mueller-Hinton agar plates before and after contact with different amounts of modified cancrinite zeolite or zeolite A.

Modified zeolite	CFU initial	Zeolite (mg)	N° UFC (24 h)
	77	2.5	0
Can-Ag	77	5.0	0
	77	10.0	0
	19	2.5	0
Can-Ag/Cu	19	5.0	0
	19	10.0	0
	64	50.0	U
Can-Cu	64	75.0	U
	64	100.0	U
	64	125.0	U
A-Ag	106	2.5	0
	106	5.0	0
	106	10.0	0
A-Ag/Cu	48	2.5	0
	48	5.0	0
	46	10.0	0
A-Cu	47	50.0	U
	47	75.0	U
	47	100.0	U
	47	125.0	U

U: uncountable

could be considered as essential microelements. Ag⁺ ions can polarize thiol, nitrogen and oxygen groups from proteins producing the precipitation and irreversible inhibition of enzymes and others important proteins. The deactivation of these enzymes produces the death of these bacteria [26, 27]. On the other hand, Cu is a bacterial nutrient, required as a cofactor by enzymes that catalyse electron transfer processes, for instance in aerobic and anaerobic respiration. To date, the inward flow of this metal ion as a nutrient and its insertion into target cuproenzymes has been reported [28]. Without these transition metal cations, a sophisticated cellular biochemistry is not possible. As a consequence, Cu²⁺ has to be imported into the bacterial cytoplasm [29].

The metallic concentration is an important factor when a bactericide should be evaluated due to its cost and environmental impact. The Ag content in zeolites such as clinoptilolites, A and X is relatively high (16.6 and 31.4 % w/w respectively) [8, 30] in comparison to cancrinites (1.5% w/w). This represents an important saving of Ag and is ecofriendly due to the Ag content must be monitored in water bodies according to Venezuelan normative [31].

On the other hand, no difference was observed in the antibacterial activity between modified cancrinite-type zeolite and zeolite A. Antibacterial properties of these solids depend on the Si/Al ratio which is the same for both zeolites.

Pseudomonas aeruginosa

Antibacterial assays were also carried out using *P. aeruginosa*. This microorganism is frequently responsible of microbial contaminations in hospitals. Table 3 reports results using different amounts of Ag⁺ or Ag⁺-Cu²⁺ modified cancrinites and zeolites A. The Cu modified solids were not assayed because they were not effective against *E. coli* which is a microorganism much more sensible to antibacterial agents than *P. aeruginosa*. Results showed an important antibacterial effect using cancrinites modified with Ag⁺. 5 mg were enough to reduce to zero the bacteria population while 20 mg were necessary for the rest of modified zeolite to reach the same result. These results showed that this bacterium is more resistant to antibacterial action than *E. coli*, probable due to its cellular wall which is much thicker than *E. coli*. Contrary to the results obtained with Ag⁺ modified cancrinite, Ag⁺ modified zeolite A was less effective against *P. aeruginosa*. These results could be attributed to a low liberation of Ag⁺ cation from zeolite A in comparison with modified Ag⁺ cancrinite. The Ag⁺-Cu²⁺ modified zeolites showed a less effectiveness than the modified Ag cancrinite. The presence of Cu²⁺ cation could be helping in the development of this microorganism due to its importance as an essential microelement.

Table 3. CFU *P. aeruginosa* determined on Mueller-Hinton culture medium agar plated before and after contact with different amounts of modified cancrinite zeolite or zeolite A.

Modified zeolite	CFU initial	Zeolite (mg)	N° UFC (24 h)
	169	5.0	0
Can-Ag	169	10.0	0
	169	20.0	0
	361	5.0	U
Can-Ag/Cu	153	10.0	1058
	164	20.0	0
	361	5.0	U
A-Ag	153	10.0	1216
	164	20.0	0
	361	5.0	U
A-Ag/Cu	153	10.0	U
	164	20.0	0

Effect of the contact time

U: uncountable

Tables 4 and 5 shows the relationship between the CFU and the contact time using *E. coli* and *P. Aeruginosa*. 2.5 mg (*E. coli*) and 20 mg (*P. aeruginosa*) of modified zeolites were used for these experiments, because they were the minimal amounts of solids that inhibited the bacterial

The contact time was varied between 14 min and 4320 min for *E. coli* while for *P. aeruginosa* ranged between 10 min and 1440 min. Table 4 shows an antibacterial effect almost instantaneous against *E. coli* and a contact time of 20 min is enough to bring down to zero the content of viable cells. These results are interesting, taking into the account that the studied solids showed bactericidal

activity not only at short time incubations but at long time treatments (three days: 4320 min).

A less value of CFU is observed in Ag-modified zeolites in comparison to those containing Ag⁺ and Cu²⁺. As we have explained before, Cu²⁺ can act as an essential microelement in the nutrition of these microorganisms.

Similar results were obtained using *P. aeruginosa*. In this case, 20 min were also enough to kill the bacterial population, however a larger amount of modified zeolites had to be used (20 mg). Evidently, this bacterium is more resistant to the assayed solids than *E. coli* as it was explained before.

Table 4. Effect of time in population growing of *E. coli*.

<i>E. coli</i>					
Time (Min).	CFU initial	Can-Ag/Cu CFU	Can-Ag CFU	A-Ag/Cu CFU	A-Ag CFU
0	92				
14	225	107	15	117	6
20	250	0	0	0	0
40	494	0	0	0	0
60	466	0	0	0	0
80	722	0	0	0	0
1440	U	0	0	0	0
1800	U	0	0	0	0
2480	U	0	0	0	0
4320	U	0	0	0	0

U: uncountable

Table 5. Effect of time in population growing of *P. aeruginosa*.

<i>P. aeruginosa</i>					
Time (min.)	CFU initial	Can-Ag/Cu CFU	Can-Ag CFU	A-Ag/Cu CFU	A-Ag CFU
0	240				
10	359	6	9	1	3
20	369	0	0	0	0
65	653	0	0	0	0
107	800	0	0	0	0
167	820	0	0	0	0
1440	U	0	0	0	0

U: uncountable

Conclusions

Sodium-nitrate cancrinite and zeolite A were ion-exchanged using: Ag^+ , Cu^{2+} and a Cu^{2+} - Ag^+ mixture. Ag^+ and Cu^{2+} - Ag^+ zeolites showed bactericidal action against *E. coli* and *P. aeruginosa* using low Ag concentrations (5 mg) and short contact time (20 min). Ag^+ binds to tissue proteins and brings structural changes in the bacterial cell membranes and cytosolic components leading to cellular distortion and death. Cu^{2+} zeolites did not show bactericidal activity, and they did not modify the growth of the reference bacterial cultures. Cu is a bacterial nutrient, required in cellular biochemistry of bacteria and in small quantities it acts as a trace element in the metabolism of the bacteria, the bactericidal effect was not observed under the used experimental conditions.

Acknowledgment

Authors are grateful to CDCH-UC and FONACIT for its financial support. Many thanks to Prof. Dr. Oscar Valbuena for checking our article.

References

- [1] Barrer R.M and Cole J.F.: "Chemistry of soil minerals. Part VI. Salt entrapment by sodalite and cancrinite during their synthesis". *J. Chem. Soc. A.*, (1970) 1516-1523.
- [2] Lindner G., Massa W and Reinen D.J.: "Structure and Properties of Hydrothermally Synthesized Thiosulfate Cancrinite". *J. Solid State Chem.*, Vol. 117, Nº 2, (1995) 386-391.
- [3] Barrer R.M., Cole J.F. and Villiger H.: "Chemistry of soil minerals. Part VII. Synthesis, properties, and crystal structures of salt-filled cancrinites. *J. Chem. Soc. A.*, (1970) 1523-1531.
- [4] Linares C. F., Simon C. and Weller M. T.: "Synthesis and characterization of the oxalate cancrinite-type zeolite". *Microporous Mesoporous Mater.*, Vol. 137, Nº 1-3, (2011) 32-35.
- [5] Linares C.F., Sánchez S., Urbina de Navarro C., Rodríguez K. and Goldwasser M.R.: "Study of cancrinite-type zeolites as possible antacid agents". *Microporous Mesoporous Mater.*, Vol. 77, Nº 2-4, (2005) 215-221.
- [6] Linares C.F., Colmenares M., Ocanto F. and Valbuena O.: "Human bile sorption by cancrinite-type zeolites". *Mater. Sci. Eng., C*, Vol. 29, Nº 1, (2009) 350-355.
- [7] Ocanto F., Linares C.F., Rivero A., Hurtado D., Guancho R. y Cardozo X.: "Un posible uso de las zeolitas cancrinita modificadas como membranas de diálisis para la adsorción de creatinina, urea y p-cresol". *Observador del Conocimiento*. Vol. 1, Nº 1, (2013) 38-45.
- [8] Rivera-Garza M., Olguín M.T., García-Sosa I., Alcántara D. and Rodríguez-Fuentes G. "Silver supported on natural Mexican zeolite as an antibacterial material". *Microporous Mesoporous Mater.*, Vol. 39, Nº 3, (2000) 431-444.
- [9] Milán Z., de Las Pozas C., Cruz M., Borja R., Sánchez E. Ilangovan K., Espinosa Y. and Luna B., "The removal of bacteria by modified natural zeolites". *J. Environ. Sci. Health., Part A*, Vol. 36, Nº 6, (2001) 1073-1087.
- [10] Inoue Y., Hoshino M., Takahashi, H., Noguchi, T, Murata T., Kanzaki Y., Hamashima H. and Sasatsu M.: "Bactericidal activity of Ag-zeolite mediated by reactive oxygen species under aerated conditions". *J. Inorg. Biochem.*, Vol. 92, Nº 1, (2002) 37-42.
- [11] Niira R, Yamamoto T., Uchida M. Antibiotic Zeolite-Containing Film. (1996). US Patent No: 5,556,699.
- [12] Kaali P, Pérez-Madriral M. M., Strömberg E., Aune R. E., Czel Gy. and Karlsson S.: "The influence of Ag^+ , Zn^{2+} and Cu^{2+} exchanged zeolite on antimicrobial and long term in vitro stability of medical grade polyether polyurethane". *eXPRESS Polym. Lett.*, Vol. 5, Nº 12, (2011) 1028-1040.
- [13] Krishnani K.K., Zhang Y., Xiong L., Yan Y., Boopathy. and Mulchandani A.: "Bactericidal and ammonia removal activity of silver ion-exchanged zeolite". *Bioresour. Technol.*, Vol.117, (2012) 86-91.
- [14] Zavareh S., Farrokhzad Z. and Darvishi F.: "Modification of zeolite 4A for use as an adsorbent for glyphosate and as an antibacterial agent for water". *Ecotoxicol. Environ. Saf.*, Vol. 155, Nº 1-8, (2018).
- [15] Yan H., Zeng X., Guo L., Lan J., Zhang L. and Cao D.: "Heavy metal ion removal of wastewater by zeolite-imidazolate frameworks". *Sep. Purif. Technol.* Vol. 194, (2018) 462-469.
- [16] Moneim M., Abdelmoneim A., Geies A. and Farghaly S.: "Synthesis, characterization and application of cancrinite in ground water treatment from Wadi El-Assiuti area, Assiut-Egypt". *Ass. Univ. Bull. Environ. Res.*, Vol. 21, Nº 1, (2018) 23-40).
- [17] Peng X., Wang C., Ma B. and Chen Y.: "Removal of Pb(II) from aqueous solution using a new zeolite-type adsorbent: Potassium ore leaching residue". *J. Environ. Chem. Eng.*, Vol. 6, Nº 6, (2018) 7138-7143.
- [18] Ocanto F., Álvarez R., Urbina de Navarro C., Lieb A. and Linares C.F.: "Influence of the alkalinity and $\text{NO}_3^-/\text{Cl}^-$ anionic composition on the synthesis of the cancrinite-sodalite system". *Microporous Mesoporous Mater.*, Vol. 116, Nº 1-3, (2008) 318-322.

- [19] Madigan M.T, Martinko J.M., Stahl D.A., Bender S., and Buckley D.: "Brock. Biología de los microorganismos". Pearson Prentice Hall. Madrid. Decimocuarta Edición 2015.
- [20] Baerlocher Ch., McCusker| L.B. and Olson D.H.: "Atlas of zeolites framework types" Ed. Elsevier, Amsterdam. Sixth Revised Edition 2007.
- [21] Treacy M.M. and Higgins J.B.: "Collection of Simulated XRD Powder Patterns for Zeolites" Ed. Elsevier, Amsterdam. Fourth Revised 2001.
- [22] Mintova S. and Barrier N.: "Verified Synthesis of Zeolitic Materials" Ed. Elsevier, Amsterdam. Third Revised Edition 2016.
- [23] Buhl J-Ch., Stief F, Fechtelkord M., Gesing T.M., Taphorn U. and Taake C.: "Synthesis, X-ray diffraction and MAS NMR characteristics of nitrate cancrinite $\text{Na}_{7.6}[\text{AlSiO}_4]_6(\text{NO}_3)_{1.6}(\text{H}_2\text{O})_2$ ". J. Alloys Compd., Vol. 305, N° 1-2, (2000) 93-102.
- [24] Flanigen E., H. Khatami, H. and Syzmansky, H.: "Infrared Structural Studies of Zeolite Frameworks". Adv. Chem. Ser., Vol 101, (1971) 201-229
- [25] Barnes MC., Addai-Mensah J. and Gerson AR.: "The mechanism of the sodalite-to-cancrinite phase transformation in synthetic spent Bayer liquor". Microporous Mesoporous Mater., Vol. 31, N° 3, (1999) 287-302.
- [26] Kwakye-Awuah B., Williams M., Kenward M. and Radecka I.: "Antimicrobial action and efficiency of silver-loaded zeolite X". J. Appl. Microbiol., Vol. 104, (2008)1516-1524.
- [27] Feng Q., Wu J., Chen G., Cui F, Kim T. and Kim J.: "A mechanistic study of the antibacterial effect of silver ions on Escherichia coli and Staphylococcus aureus". J. Biomed. Mater. Res., Vol. 52, N° 4, (2000) 662-668.
- [28] Stewart L.; Thaqi D., Kobe B, McEwan A, Waldron K. and Djoko.: "Handling of nutrient copper in the bacterial envelope". Metallmics., Vol. 11, (2019) 50-63.
- [29] Nies D.: "The biological chemistry of the transition metal "transportome" of Cupriavidus metallidurans". Metallmics., Vol. 8, (2016) 481-507.
- [30] Demirci S., Ustaoglu Z., Yilmazer G., Sahin F. and Baç N.: "Antimicrobial Properties of Zeolite-X and Zeolite-A Ion-Exchanged with Silver, Copper, and Zinc Against a Broad Range of Microorganisms" Appl. Biochem. Biotechnol., Vol. 172, N° 3, (2014) 1652-1662
- [31] Gaceta Oficial Extraordinaria de la República de Venezuela N° 5.021 Decreto N° 883. "Normas para la Clasificación y el Control de la Calidad de los Cuerpos de Agua y Vertidos o Efluentes Líquidos" (1995).



UNIVERSIDAD
DEL ZULIA

REVISTA TECNICA

DE LA FACULTAD DE INGENIERIA
UNIVERSIDAD DEL ZULIA

Vol. 42. N°3, Septiembre - Diciembre 2019, pp. 104 -151 _____

*Esta revista fue editada en formato digital y publicada en
Septiembre de 2019, por el **Fondo Editorial Serbiluz,**
Universidad del Zulia. Maracaibo-Venezuela*

**www.luz.edu.ve
www.serbi.luz.edu.ve
produccioncientifica.luz.edu.ve**